

U. S. Department of Energy LOW TEMPERATURE GEOTHERMAL MINERAL RECOVERY PROGRAM

Magnetic Partitioning Nanofluid for Rare Earth Extraction from Geothermal Fluids

Interim Technical Report Submitted by
Pacific Northwest National Laboratory
In Collaboration with
Global Seawater Extraction Technologies

Technical Contact	Business Contact
Dr. B. Peter McGrail Pacific Northwest National Laboratory P.O. Box 999, MS K4-18 Richland, WA 99352	Ms. Sheena Kanyid Pacific Northwest National Laboratory P.O. Box 999, MS K5-08 Richland, WA 99352

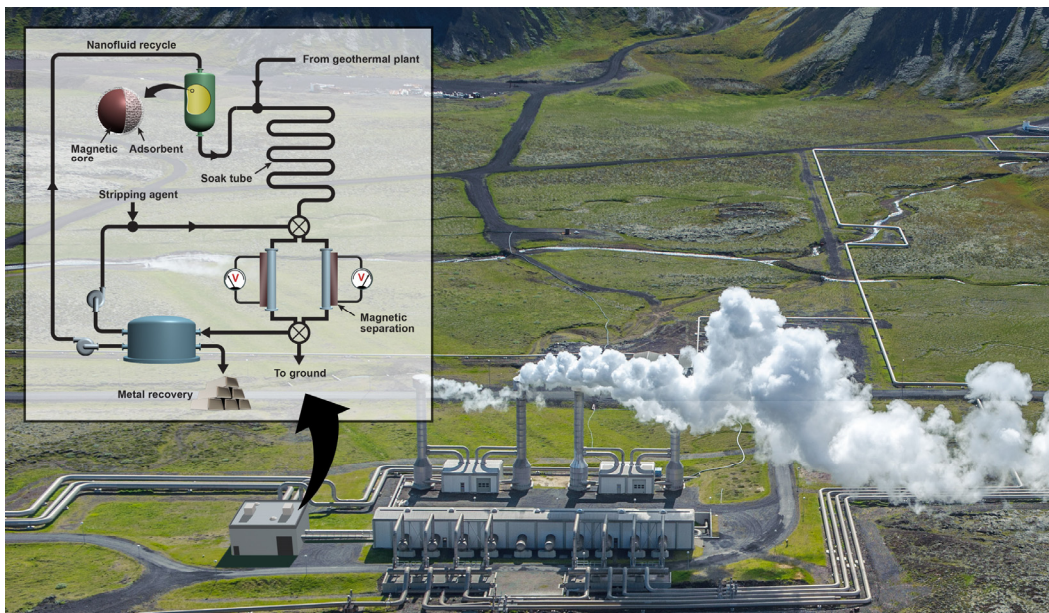


Table of Contents

1.0	Project Overview	1
2.0	Technical Progress Summary	2
2.1	MOF Sorbent	2
2.2	Silica Sorbent.....	3
2.3	Techno-Economic Performance Analysis	5
2.3.1	Adsorbent Performance.....	5
2.3.2	Cost comparison.....	6
2.3.3	Complete Process TEA	7
3.0	Summary and Conclusion.....	10

1.0 PROJECT OVERVIEW

Rare earth metals are critical materials in a wide variety of applications in generating and storing renewable energy and in designing more energy efficient devices [1]. Extracting rare earth metals from geothermal brines is a very challenging problem due to the low (ppb) concentrations of these elements and engineering challenges (pressure drop, parasitic pumping power losses) with traditional chemical separations methods involving packed sorbent beds or membranes that would impede large volumetric flow rates (>6000 gal/min for a 20 MWe plant) of geothermal fluids transitioning through the plant [2]. In addition, to achieve reasonable brine residence times, the packed bed or membrane systems would be very large and so pose significant challenges in fitting within an existing geothermal plant footprint and would have very high capital and operating costs.

In this project, we are demonstrating a simple and highly cost-effective nanofluid-based method for extracting rare earth metals from geothermal brines that is illustrated in Figure 1. Core-shell composite nanoparticles are produced that contain a magnetic iron oxide core surrounded by a shell made of silica or metal organic framework (MOF) sorbent functionalized with chelating ligands selective for the rare earth elements. By introducing the nanoparticles at low concentration (≈ 0.05 wt%) into the geothermal brine after it passes through the plant heat exchanger, the brine is exposed to a very high concentration

of chelating sites on the nanoparticles without need to pass through a large and costly traditional packed bed or membrane system where pressure drop and parasitic pumping power losses are significant issues. Instead, after a short residence time flowing with the brine, the particles are effectively separated out with an electromagnet and standard extraction methods are then applied to strip the rare earth metals from the nanoparticles, which are then recycled back to the geothermal plant.

Recovery efficiency for the rare earths have now been measured for both silica and MOF sorbents functionalized with a variety of chelating ligands and the results used to conduct a preliminary but detailed techno-economic performance analysis of extraction systems using both sorbents. Production cost estimates confirm potential to produce REEs at less than half the present commodity market value for these metals generating an $IRR \geq 20\%$, clearly indicating that continuation into Budget Period 2 is warranted.

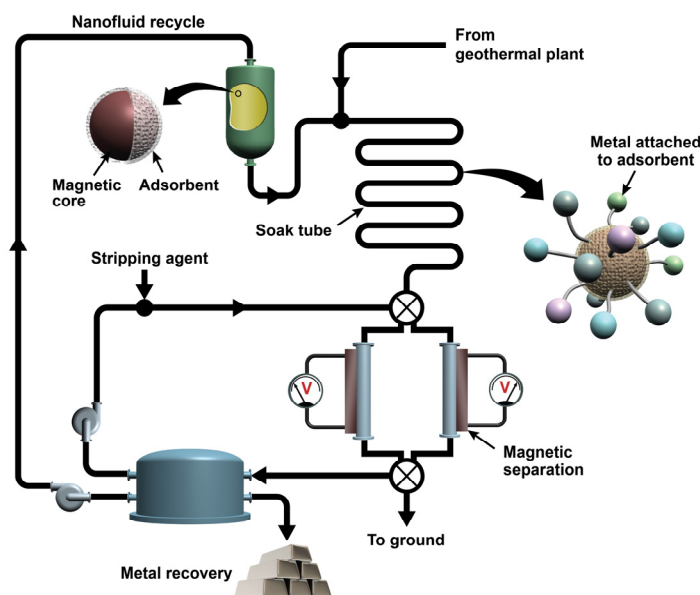


Figure 1. Conceptual drawing of magnetic partitioning nanofluid extraction system

2.0 TECHNICAL PROGRESS SUMMARY


Technical progress made under the first year of the project is summarized below.

2.1 MOF Sorbent

For brevity, we will not describe the full suite of MOF synthesis and functionalization trials that were conducted as these have been documented in our quarterly reports. Here, we will report on the three most promising sorbents. Several highly aqueous stable zirconium- and chromium-based MOFs functionalized with a high density of chelating groups ($-\text{COO}^-$, CO_2^- , $-\text{SO}_3^-$, PO_3^{2-} , $-\text{C}(\text{NOH})-\text{NH}_2$) were synthesized and characterized. Batch experiments were performed by introducing synthesized MOFs to 0.005 M and 0.0005 M solutions of REE's at pH 3 to 4. REE uptake was determined by comparing ICP-OES analysis of blank reference solution samples where no sorbent was present with solution samples extracted after 5 min exposure to the MOF sorbent. Based on the ICP-OES data, the UIO-66 (COO^-)₂ MOF (Table 1) is found to be a reasonably good sorbent reaching up to a maximum of 122 mg/g (Eu) versus our 50 mg/g proposed target for the MOF based sorbents. Please note that we did not attempt to synthesize nanoparticle forms of the MOFs for these initial trials. The UIO-66 MOF and other MOFs reported on here were fine powders on the order of 50 μm diameter. Given that our target is to have particles 1000X smaller with proportionally higher surface area, these loadings are extremely encouraging.

Table 1. REE Uptake with UIO-66 (COO^-)₂: 0.005 M REE


REE	Loading (mg/g)	%Removal	K_d
Nd	121.6	31.4	246.41
Dy	28.7	6.83	49.3
Eu	122.5	16.78	190.22
Ce	79.03	11.46	109.78
Y	99.08	20.2	242

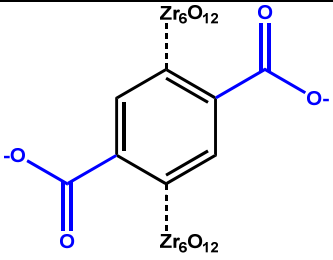

The MOF MIL-101 was functionalized with the chelating group ($-\text{SO}_3^-$) and tested under identical conditions except that REE concentration was reduced 10X to 0.0005 M. The ICP-OES data (Table 2) shows the MIL-101 functionalized with $-\text{SO}_3^-$ has over 90% removal efficiency with distribution coefficient reaching up to 40,000 mL/g (Dy) suggesting promise to quantitatively strip REEs from geothermal brines at ppb concentration.

Table 2. REE Uptake with MIL-101 SO_3Na : 0.0005 M REE


REE	Loading (mg/g)	%Removal	K_d
Y	29.07	88.54	7728
Nd	64.09	94.5	12866
Dy	59.9	97.7	36244
Eu	71.64	95.99	21776
Ce	35.89	96.2	21033

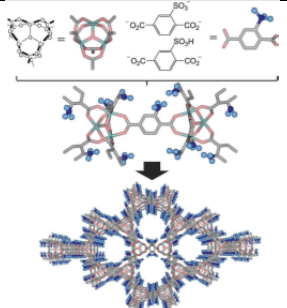

Last, we covalently attached diethylene triamine (DETA) to an In-MOF by reacting with free carboxyl groups present on the periphery of this sorbent as illustrated in Table 3. Experiments were conducted on this functionalized MOF under identical conditions as described previously. The batch experiments show this MOF to have the highest REE extraction performance with quantitative removal after 5 minutes of exposure.


Table 3. REE Uptake with In-MOF DETA: 0.0005 M REE

REE	Loading (mg/g)	%Removal	K_d
Y	23.3	99.98	2328440
Nd	57.35	99.99	-
Dy	25.12	99.75	140027
Eu	53.96	99.98	5395081
Ce	31.45	99.99	791970

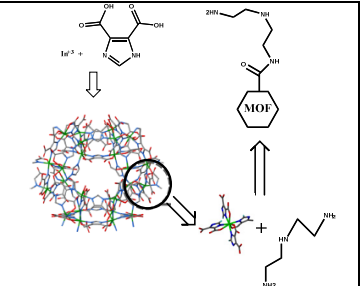

2.2 Silica Sorbent

The functional groups listed in Figure 2 were selected because they have been previously demonstrated to adsorb heavy metal ions with very high adsorption capacities. Silica particle cores were functionalized using the methods illustrated in Scheme 1. All the functionalized materials prepared were thoroughly characterized by IR, PXRD, SEM and BET surface area measurements. Dried powders were redispersed into solution as agglomerates with estimated particle sizes of approximately 50 μm .

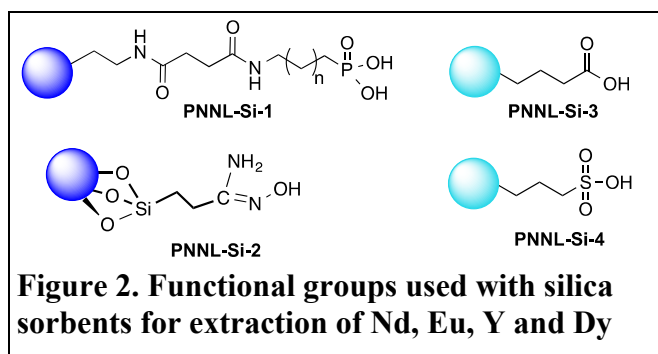

A total of eight sorbents were evaluated for REE uptake as listed in Table 4. Systems 5-7 provided for some reproducibility assessment with different batches. SiO_2 -PNNL-4 included both amino groups as well amidoxime functional groups. Sorption experiments were carried out using similar batch methods as for the MOF sorbents described previously. In brief, a specific amount of functionalized silica was mixed with 10 mL of 0.005 M aqueous salt solutions and allowed to soak for 5 min. After the specified contact time, the mixtures were filtered using 0.2 micron filter to remove functionalized silica from supernatant salt solution. The residual concentration of rare earth metal ions in the supernatant was determined by ICP-OES.

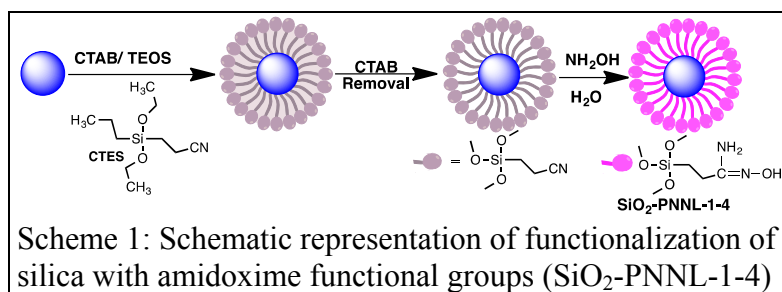


Table 4. Functionalized silica systems used for adsorption studies

	Systems	Functional group
1	Propylcarboxylic acid functionalized silica	carboxylic acid
2	Ethyl/butyl phosphonic acid silica	phosphonic acid

3	3-Propylsulfonic acid functionalized silica	sulfonic acid
4	3-(Ethylenediamino)propyl-functionalized silica	amino
5	SiO ₂ -PNNL-1	amidoxime
6	SiO ₂ -PNNL-2	amidoxime
7	SiO ₂ -PNNL-3	amidoxime
8	SiO ₂ -PNNL-4	amidoxime, NH ₂

The calculated adsorption uptake of Nd, Eu, Y and Dy is given in Table 5. Carboxylic acid, phosphonic acid, sulphonic acid and amino functionalized silica exhibited higher adsorption capacities for Eu (53-71 mg/g) compared to neodymium (15-50 mg/g) at 5 min residence times.

Table 5. REE Uptake Measurement Results for Functionalized Silica

Sample #	Metal Salt/ Silica Sorbent	Uptake (mg/g)	% Removal
1	Neodymium(III) nitrate hexahydrate	NA	
2	Propylcarboxylic acid functionalized silica	15.30	2.05
3	Ethyl/butyl phosphonic acid Silica	49.70	6.80
4	3-Propylsulfonic acid-functionalized silica	-1.10	-0.16
5	3-(Ethylenediamino)propyl-functionalized silica	21.30	2.85
6	Europium(III) nitrate pentahydrate	NA	NA
7	Propylcarboxylic acid functionalized silica	53.80	7.23
8	Ethyl/butyl phosphonic acid Silica	65.80	9.54
9	3-Propylsulfonic acid-functionalized silica	58.60	8.64
10	3-(Ethylenediamino)propyl-functionalized silica	71.90	10.49
11	Neodymium(III) nitrate hexahydrate	NA	NA
12	SiO ₂ -PNNL-1	47.40	6.35
13	SiO ₂ -PNNL-2	23.30	3.33
14	SiO ₂ -PNNL-3	62.50	8.64
15	SiO ₂ -PNNL-4	48.60	7.10
16	Europium(III) nitrate pentahydrate	NA	NA
17	SiO ₂ -PNNL-1	29.50	3.97
18	SiO ₂ -PNNL-2	13.60	1.90
19	SiO ₂ -PNNL-3	36.60	5.01
20	SiO ₂ -PNNL-4	3.70	0.52
21	Yttrium(III) nitrate hexahydrate	NA	NA
22	SiO ₂ -PNNL-1	-0.60	-0.13
23	SiO ₂ -PNNL-2	28.20	6.27
24	SiO ₂ -PNNL-3	5.40	1.28
25	SiO ₂ -PNNL-4	2.70	0.61
26	Dysprosium(III) nitrate hydrate	NA	NA
27	SiO ₂ -PNNL-1	-7.20	-1.34
28	SiO ₂ -PNNL-2	-2.70	-0.50

Sample #	Metal Salt/ Silica Sorbent	Uptake (mg/g)	% Removal
29	SiO ₂ -PNNL-3	37.90	7.04
30	SiO ₂ -PNNL-4	-13.50	-2.71

2.3 Techno-Economic Performance Analysis

The objective of this task is to analyze the techno-economic performance of the rare earth metal extraction process using magnetic nanofluids. Costs for the magnetic nanoparticle adsorbents were estimated based on the raw material costs and complexity of the preparation processes. The performance of the MOFs and modified silica adsorbents were also projected for designed parameters based on the available data presented previously. Capital and operating costs, including energy, equipment, labor, taxes and depreciation were determined using a pre-set calculation template for the nanofluid extraction process.

2.3.1 Adsorbent Performance

Because the screening adsorption experiments could not be conducted under the exact conditions expected in the real system, extrapolation methods were used to project REE adsorption capacity under typical geothermal brine REE concentrations (ppb level) and shorter contact times on the order of <1 min. The particle sizes of the tested adsorbents are around 50 μm and the contact time between the REE solution and adsorbents was 5 min. For the same mass of sorbent, the surface area is increased 1000X when the particle size is reduced to 50 nm in the actual extraction system. Consequently, we will use this scaling factor to adjust for both shorter contact time and lower REE concentrations in the actual situation. However, not all of the surface area will be available to chelate REE metal ions due to diffusion time required to access the interior pore surfaces. So an adjustment factor of 0.2 is applied reducing the scaling factor to 200X for the 50 nm nanoparticles. With these assumptions, the projected loading of selected REE metal ions for some MOF candidates at typical geothermal brine conditions are summarized in Table 6. In the last row, the required adsorbent mass was calculated for all the metals based on the projected loadings and assuming 90% of metal ions will be removed. We have conservatively assumed that incremental adsorbent is needed to remove all of the five REE candidates, i.e. the required sorbent mass is the summation of the required adsorbent mass for each REE metal. When the data is not available for all five REE metals, the results were normalized to calculate the maximum adsorbent mass. The estimated maximum adsorbent mass needed for the MIL-SO₃Na and DETA In-MOF are 3.9 kg and 5.6 kg, respectively. For reference, our estimated required sorbent mass in the original proposal was 7.4 kg.

Table 6. Projected REE metal loadings and estimated adsorbent mass for MOFs

MOF sample REE	MIL-SO ₃ Na (mg/g)	In-MOF(mg/g)	DETA at In-MOF(mg/g)	UiO-66 (COO) ₂ (mg/g)
Y	2.62	1.98	2.10	0.89
Nd	2.37	0.44	2.12	0.45
Dy	0.29	0.11	0.12	0.01
Eu	0.19	-	0.14	0.03
Ce	3.42	1.84	2.99	0.75
Adsorbent (kg)	3.9	8.6	5.6	30.2

Similar projections were made for REE extraction at typical geothermal brine conditions for the modified silica sorbent. Only the samples with experimental data on multiple REE metal ions

were selected and the maximum adsorbent masses were calculated after normalization. The results are summarized in Table 7. It is clear that the projected loadings for modified silica are smaller compared to the best MOF candidates shown in Table 6. The two best silica candidates are ethyl phosphonic acid modified silica and SiO₂-PNNL-2. The estimated maximum adsorbent mass needed for those two modified silica are 36.8 kg and 42.3 kg, respectively. We now turn to the development of extraction cost comparisons for the MOFs and modified silica adsorbents.

Table 7. Projected REE metal loadings and estimated adsorbent mass for modified silica

Silica sample REE	Propylcarboxylic acid-silica (mg/g)	Ethly phosphonic acid-silica (mg/g)	3-Propylsulfoneic acid-silica (mg/g)	SiO ₂ -PNNL-2 (mg/g)
Y	-	0.27	0.05	-
Nd	0.06	0.19	-	0.24
Dy	-	-	0.03	-
Eu	0.02	0.02	0.02	0.01
Ce	-	-	-	-
Adsorbent (kg)	85	36.8	100.2	42.3

2.3.2 Cost comparison

It is necessary to synthesize the magnetic core nanoparticles in bulk to significantly reduce cost. Assuming a reported procedure can be scaled up to synthesize Fe₃O₄ nanoparticles with size of 13-20 nm¹, the cost was estimated to be \$34.4/kg as shown in Table 8. The cost includes cost of chemicals, energy, equipment, and labor. The labor cost is the major factor because of the batch reaction.

Table 8. Estimated cost to prepare Fe₃O₄ nanoparticles with size from 13-20 nm in kg level

Material	Energy	Separation	Equipment	Labor	Total
\$3.14/kg	\$1.26/kg	\$2.64/kg	\$5.21/kg	\$22.22/kg	\$34.4/kg

The costs of the adsorbents will be estimated using the material costs, labor costs, processing costs, and modification costs. The labor cost is estimated to be \$22/kg similar to that of the Fe₃O₄ nanoparticles and the processing cost is estimated to be two times of the material cost. The modification cost will be estimated as 50% of the total cost of the base adsorbent including labor cost, processing cost and material cost. There will be no modification cost for the adsorbents that do not need modification. The yield and magnetic core cost will also be considered and included into the cost. The core-shell preparation cost will be estimated to be 20% of the magnetic nanoparticles cost.

A general formula can be written as below:

$$\begin{aligned}
 & \text{Adsorbent cost} = \frac{\{[(\text{Metal salt cost} + \text{Organic linker cost} + \text{Solvent cost} + \text{Other cost}) \times 3 + \text{Labor cost}] \times (1 + 50\%) \div \text{Yield} + \text{Fe}_3\text{O}_4 \text{ cost}\} \times (1 + 20\%)}{\text{Modification cost} \quad \quad \quad \text{Core-shell cost}}
 \end{aligned}$$

Material cost

Using the strategy described above, the adsorbent cost for all the four candidates are calculated and summarized in Table 9. Together with the required maximum adsorbent mass estimated in Section 2.3.1, the estimated total annual adsorbent costs were also included in the table assuming 6000 hour lifetime for all the adsorbents.

Table 9. Estimated cost to prepare and use magnetic core-shell nano-adsorbent

	Metal (\$/kg)	Linker (\$/kg)	Solvent (\$/kg)	Other (\$/kg)	Labor (\$/kg)	Yield	Fe ₃ O ₄ (\$/kg)	Adsorbent cost (\$/kg)	Adsorbent mass (kg)	Total adsorbent cost (\$/year)
DETA at In-MOF	0.9	171.8	142.9	0.8	22	0.90	34.4	1983.68	5.6	16219
MIL-SO ₃ Na	1	110	99	0.25	22	0.90	34.4	911.61	3.9	5191
Ethly phosphonic acid-silica	9.4	0.77	36.1	44	22	0.95	34.4	596.08	36.8	32026
SiO ₂ -PNNL-2	9.4	0.77	36.1	90	22	0.95	34.4	857.55	42.3	52961

In the proposal, we provided a table to illustrate the cost impact when considering recovery of multiple REE metals using the nanofluid extraction process. Here we will update the table with the new adsorbent costs and metal sale prices using the four best candidates from the results above and the results are shown in Table 10. According to the data in the table above, the drop in the sale prices for the REE metals actually did reduce the potential annual revenue by about 14% from \$935,216/year to \$806,371/year. Comparing to the original guess of the cost of nanoparticles at \$800/kg, the estimated cost for all the adsorbent candidates are pretty close except for the DETA In-MOF. However, the difference in the annual material cost for the candidates are within reasonable range at this early R&D stage. So it seems reasonable to carry further study for all the four adsorbent candidates to find out the best adsorbent and optimized the working conditions.

Table 10. Updated cost impacts using the nanofluid extraction process

Parameter		Ce	Dy	Eu	Nd	Y
Recovery Efficiency	90%					
Brine Flow Rate (gal/min)	6000					
Metal Concentration in Brine (ppb)		500	30	15	200	300
Metal Production Rate (kg/yr)	12235	5854	351	176	2342	3512
Metal Sales Price \$/kg		10	475	1000	83	60
Annual Revenue \$	\$806,371	\$58,540	\$166,725	\$176,000	\$194,386	\$210,720
Adsorbent candidate	DETA at In-MOF	MIL-SO ₃ Na	Ethly phosphonic acid-silica	SiO ₂ -PNNL-2		
Nanoparticle Charge (kg)	5.6	3.9	36.8	42.3		
Nanoparticle lifetime (h)	6000	6000	6000	6000		
Nanoparticle cost (\$/kg)	1983.7	911.6	596.1	857.6		
Metal Recovery Cost \$/kg	5.6	5.6	5.6	5.6		
Annual Material Cost \$	\$84,735	\$73,707	\$100,543	\$121,480		
Annual Raw Profit \$	\$721,636	\$732,664	\$705,828	\$684,891		

2.3.3 Complete Process TEA

2.3.3.1 Flowsheet and equipment

The magnetic nanofluid extraction process for the rare earth metals can be modeled in the flowsheet shown in Figure 3. Basically, the magnetic nanofluid is mixed with the feed brine and then the mixture passes through pipes that provide residence time to extract REE. Then the nanoparticles are separated out from the brine using electromagnetic force. Two magnetic separators are placed to make the separation a continuous process. Strip agent will be used to desorb the REE and regenerate the magnetic nanoparticles.

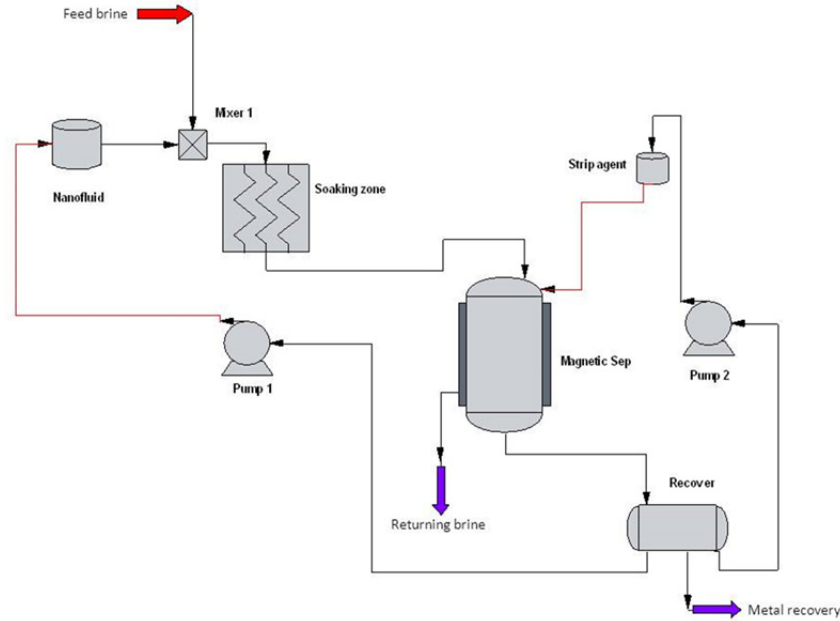


Figure 3. Rare earth metal extracting process using magnetic nanofluids

The necessary equipment for this process is listed Table 11 below.

Table 11. Estimated cost for the equipment in the magnetic nanofluid extraction process

ID	Qu.	Equipment	Size	units	Cost Basis		Scaling Factor	Installation Factor	Current Cost	Installed Cost (each)		Installed Costs (ISBL)
					Cost	Year				(low risk)		
1	1	Pump 1 for nanofluid	1.5	kW	\$ 1,280	2015	0.7	2	\$ 1,941	\$ 3,883	\$ 4,582	
2	1	Pump 2 for stripe agent	1.5	kW	\$ 1,280	2015	0.7	2	\$ 1,941	\$ 3,883	\$ 4,582	
3	1	Residence tube	35.6	m	\$ 53,400	2015	0.7	2	\$ 80,991	\$ 161,982	\$ 191,139	
4	2	Separator and magnets	7.6	m ³	\$ 8,000	2015	0.7	2	\$ 12,133	\$ 24,267	\$ 57,270	
5	1	Vessel for nanofluid	13.6	m ³	\$ 5,000	2015	0.7	2	\$ 7,583	\$ 15,167	\$ 17,897	
6	1	Vessel for stripe agent	1.4	m ³	\$ 2,500	2015	0.7	2	\$ 3,792	\$ 7,583	\$ 8,948	
7	1	Vessel for recovery	1.36	m ³	\$ 34,675	2015	0.7	2	\$ 52,591	\$ 105,182	\$ 124,115	
8	1	Miscellaneous Tube and valves	1	m ³	\$ 20,000	2015	0.7	2	\$ 30,334	\$ 60,667	\$ 71,587	

Costs were estimated using the method of Guthrie, which generally includes four steps:²

1. Sizing the reactor or vessel based on the known flow rates and assumed residence time
2. Estimating purchase cost based on empirical design data (Year 2002) (Williams power law)*
3. Estimating total cost by including the installation module factor: 2.0 (includes labor, piping and accessories cost)
4. Converting to today's cost by considering the Chemical Engineering Plant Cost Index: 2002 (395.6) vs. 2015 (600, estimated)

The total installed equipment cost was estimated to be \$480,119.

2.3.3.2 Capital and Operating Costs

The capital and operation costs were estimated using a calculation template that was provided by ARPA-E for use on another project requiring cost estimation for a chemical processing plant.

Reasonable complexity was added to simulate cost analysis for a practical project.³⁻⁹ The capital investment estimated results are shown in Table 12.

Table 12. Capital investment summary for the magnetic nanofluid extraction process

Installed Costs (ISBL+)			\$ 480,119
Auxiliaries	30.0% of ISBL+	\$	144,036
Buildings	20.0% of ISBL+	\$	96,024
Site development	5.0% of ISBL+	\$	24,006
Land	2.5% of ISBL+	\$	11,855
Spare parts	0.5% of ISBL+	\$	2,401
Fixed Capital Investment (FCI)		\$	758,440
Working Capital	19.0% of FCI	\$	144,104
Start-up Costs	8.0% of FCI	\$	60,675
Total Capital Investment (TCI)		\$	963,219

Similarly, the operation expense for the magnetic nanofluid process is summarized in Table 13. The plant was assumed to be running at 95% capacity factor. The labor and utility costs were positively related with this capacity factor. It is observed that the labor related costs were the major cost for daily operation. The raw material cost included the adsorbent cost and the metal recovery cost. Here, the MIL-SO₃Na was selected as an example in the raw material cost.

Table 13. Operation expense summary for the magnetic nanofluid extraction process

Plant capacity factor			95%
Fixed Costs			
Maintenance	5.0% of FCI	\$	37,922
Operating Labor (OL)	25 FTEs	\$	208,050
Laboratory Costs	10.0% of OL	\$	20,805
Supervision	20.0% of OL	\$	41,610
Plant Overheads	30.0% of OL	\$	62,415
Insurance	1.0% of FCI	\$	7,584
Royalties	1.0% of FCI	\$	7,584
Variable Costs			
Raw Materials (RM)		\$	73,707
Miscellaneous Materials	10.0% of RM	\$	7,371
Utilities			5,344
Indirect Costs	10.0% of Costs	\$	47,239
Annual Operating Costs		\$	519,632

2.3.3.3 Financial analysis and IRR

Financial analysis was conducted using the previous capital and operation costs. The results are summarized in Table 14. The production and values of different REE metals were normalized into one product to facilitate the analysis. The annual total production of REE was estimated to be 12,235 kg and the average value for the REE was estimated to be \$65.9/kg based on the conditions listed in Table 10. The plant operation time was assumed to be 30 years and the payment time for debt was assumed to be 10 years. The IRR was calculated to be 20% for the MIL-SO₃Na using the capital costs and corresponding operation costs. The IRRs for other adsorbents DETA In-MOF, ethly phosphonic acid-silica, and amidoxime-silica were estimated to be 19%, 17%, and 15%, respectively.

Table 14. Financial analysis for the magnetic nanofluid extraction process

Parameters			
FCI			\$ 758,440
TCI			\$ 963,219
Debt		45%	
Equity		55%	
Interest on debt		4.5%	
Preferred dividend rate		0.00%	
Repayment term of debt		10 years	
Capital Expenditure Period		3 years	
completion in year	0	0%	
completion in year	1	10%	
completion in year	2	60%	
completion in year	3	30%	
completion in year	4	0%	
completion in year	5	0%	
Operation begins at year		4	
Operational Period		30 years	
Ramp Up Period			
capacity in year	4	100%	
capacity in year	5	100%	
capacity in year	6	100%	
Escalation of O&M, fuel, revs		3.00%	
Discount rate		10.00%	
Capital Cost Escalation prior to operation		0.397%	
Capital Depreciation period		20 years	
Depreciation X-declining balance		150%	
Corporate Tax Rate (fed+state)		38%	
Effective Annual Rate of Equity			
Cost of Capital			
Cost-Year Dollars		2015	
WACC		12.29%	
IRROE		20%	

3.0 SUMMARY AND CONCLUSION

Adsorbent performance at typical geothermal brine conditions for both MOFs and modified silica materials were projected based on currently available data. The adsorbent costs were estimated based on material cost and modification complexity. The MOF sorbents offer the best tradeoff in terms of sorbent performance and balance of plant capital and operations costs. However, the differences in IRR between the best MOF and best silica candidate ended up being relatively small. Looking forward, the benefit of that finding is that if an unexpected problem develops during development of the MOF sorbent, a switch to the silica sorbent can be done relatively easily and with little impact on overall economics of the process.

A quite conservative financial analysis of the complete nanofluid REE extraction process was conducted and an IRR of about 20% was estimated for the best candidate sorbent. This exceeds our goal to project a 15% IRR for the process. Further work justifying less conservative assumptions is likely to improve this first IRR estimate. In summary, the work conducted under Budget Period 1 clearly supports proceeding with R&D to further develop the nanofluid REE extraction process and demonstrate cycle performance and lifetime of the nano-sorbents under more realistic operating conditions.

References

- 1) Kolen'ko et al., *J. Phys. Chem. C* **2014**, *118*, 8691-8701.
- 2) *Plant design and economics for Chemical Engineers*. Max S. Peters. McGraw Hill, 2003.
- 3) *Perry's Chemical Engineers' Handbook*, seventh edition. Perry and Green, Process Economics, section 9.
- 4) *Conceptual Design of Chemical Processes*. Douglas McGraw Hill (1988) chapter 2.
- 5) Individual Factor Method; Silla, "Chemical Process Engineering: Design and Economics"
- 6) Operating costs adapted from; Moulijn, "Chemical Process Technology", Process Evaluation chapter.
- 7) Module Factor Method from: Turton, Bailie, Whiting, Shaeiwitz, "Analysis, Synthesis and Design of Chemical Processes".
- 8) NETL publication DOE/NETL-401/090808
- 9) NIPPON Steel Technical Report, "Technology Trend of Titanium Sponge and Ingot Production", No. 85 (January 2002).